

Enhancing the thermal properties of paraffin wax as latent heat storage material using hybrid nanomaterials

A. A. El-Sebaï¹, S. Aboul-Enein¹, M. R. I. Ramadan¹, N. Samy¹, A. R. El-Sayed², S. M. Shalaby^{2,*}

¹ Physics Department, Faculty of Science, Tanta University, Tanta 31511, Egypt

² Engineering Physics and Mathematics Department, Faculty of Engineering, Tanta University, Tanta 31511, Egypt

* Corresponding author: S. M. Shalaby, saleh.shalaby@f-eng.tanta.edu.eg

CITATION

El-Sebaï AA, Aboul-Enein S, Ramadan MRI, et al. Enhancing the thermal properties of paraffin wax as latent heat storage material using hybrid nanomaterials. *Characterization and Application of Nanomaterials*. 2024; 7(1): 4912. <https://doi.org/10.24294/can.v7i1.4912>

ARTICLE INFO

Received: 29 February 2024

Accepted: 25 March 2024

Available online: 18 April 2024

COPYRIGHT



Copyright © 2024 by author(s).

Characterization and Application of Nanomaterials is published by EnPress Publisher, LLC. This work is licensed under the Creative Commons Attribution (CC BY) license.

<https://creativecommons.org/licenses/by/4.0/>

Abstract: Paraffin wax is the most common phase change material (PCM) that has been broadly studied, leading to a reliable optimal for thermal energy storage in solar energy applications. The main advantages of paraffin are its high latent heat of fusion and low melting point that appropriate solar thermal energy application. In addition to its accessibility, ease of use, and ability to be stored at room temperature for extended periods of time, Nevertheless, improving its low thermal conductivity is still a big, noticeable challenge in recently published work. In this work, the effect of adding nano-Cu₂O, nano-Al₂O₃ and hybrid nano-Cu₂O-Al₂O₃ (1:1) at different mass concentrations (1, 3, and 5 wt%) on the thermal characteristics of paraffin wax is investigated. The measured results showed that the peak values of thermal conductivity and diffusivity are achieved at a wight concentration of 3% when nano-Cu₂O and nano-Al₂O₃ are added to paraffin wax with significant superiority for nano-Cu₂O. While both of those thermal properties are negatively affected by increasing the concentration beyond this value. The results also showed the excellence of the proposed hybrid nanoparticles compared to nano-Cu₂O and nano-Al₂O₃ as they achieve the highest values of thermal conductivity and diffusivity at a weight concentration of 5.0 wt%.

Keywords: thermal characteristics; phase change materials; paraffin wax; hybrid nanocomposites

1. Introduction

Paraffin wax (PW) is one of the most important materials used as phase change materials (PCMs) in the thermal energy storage system [1]. A lower thermal conductivity is considered the main disadvantage of PCMs, which causes a lower heat transfer rate during the charging and discharging processes. Many studies have been conducted to overcome this property, such as adding metallic or nonmetallic nanoparticles with high thermal conductivity [2], inserting fins [3], fibrous materials [4], macro-micro and nano-encapsulations [5,6], metal foams [7], carbon nanotubes [8].

The above-mentioned techniques used to improve the thermal conductivity of the PW include the addition of high-conductive nanomaterials, which is the simplest and most practicable technique. The influence of adding nano-graphite (NG) on the PW thermal conductivity was experimentally studied by Li [9]. The results showed that the thermal conductivity of the composite PCMs with 1% and 10% NG is 2.89 times and 7.41 times that of pure paraffin. Nano-Silicon nitride (Si₃N₄) at different mass fractions (1, 2, 3, 4, 5, 10 wt%) was studied by Yang et al. [10] to enhance the thermal properties of PW. They observed an improvement of 35% in thermal conductivity and also found an improvement in thermal diffusivity, reaching 47% at 10 wt% Si₃N₄

additional fraction. Wang et al. [11] experimentally studied the effect of dispersing copper oxide (CuO) as a nanomaterial at different mass fractions of 0.3, 0.6, 0.9, and 1.2% into the PW. They concluded that the thermal conductivity of nanocomposite PCMs with a weight fraction of 1.2% had improved by 24.4%. Pise et al. [12] experimentally evaluated the improvement of thermal performance of PW integrated with nano-alumina (Al_2O_3) particles at various mass concentrations of nanoparticles of 1, 3, and 5%. They reported that the thermal performance of paraffin wax is enhanced up to 14% compared to pure paraffin. Another experimental study concerning the thermophysical properties of Al_2O_3 nanoparticles/paraffin emulsions with two mass fractions of 5 wt% and 10 wt% [13]. The measured results showed that the increase in thermal conductivity is nonlinear with the increase in nanoparticle mass fraction. Yanqi et al. [14] examined how interfacial thermal resistance and particle size affected the thermal conductivity of paraffin/expanded graphite (EG) composites. They found that the increase in thermal conductivity is directly correlated with larger particle sizes. The small EG particles have less of an enhancement in thermal conductivity because interfacial thermal resistance predominates in their impact on the composite thermal conductivity. Sari et al. [15] also examined the paraffin/EG composite material and revealed that the thermal conductivity of the composite increased to 0.82 W/mK at 10 wt% EG. Huang et al. [16] investigated the enhancement of thermal conductivity of paraffin composites using non-equilibrium molecular dynamics simulation. The simulation results indicated that the thermal conductivity of PW is significantly enhanced by adding graphene oxide, which is more efficient than graphene. Maher et al. [17] investigated the effect of the addition of nanosilicon carbide (SiC) and nanosilver (Ag)-based paraffin composites on the thermal characteristics of PCM. The results revealed that the thermal conductivity of the paraffin/SiC composite improved by 58.2%, which is much higher than the thermal conductivity of the paraffin/Ag composite, which improved by 31.2% at the same mass fraction of 15 wt%. Qusay et al. [18] found that the thermal conductivity of the PW is improved by 18.2% when adding 3 wt% of nano-SiC into the PW. The impact of silver nanoparticles on the thermal conductivity of the PW was experimentally studied by Pradeep et al. [19]. Their results showed that thermal conductivity increases with the increase of the mass concentration of Ag nanoparticles. Sahan et al. [20] concluded experimental research evaluating the effect of adding nanomagnetite (Fe_3O_4) on the thermal properties of PW. They found that the thermal conductivity increased by 48% and 67% when adding 10 wt% and 20 wt% nano magnetite, respectively.

According to several studies, PCM could benefit from the addition of two or more hybrid nanoparticles [21–23]. When hybrid nanoparticles are used instead of single nanoparticles, the researchers conclude that the thermal conductivity increases at the same additional mass fraction compared to individual nanoparticles. From this point forward, several practical, numerical, and experimental investigations focus on the use of hybrid nanoparticles. Kumar et al. [24] studied the influence of hybrid nanoparticles containing SiO_2 and CeO_2 nanoparticles on the thermo-physical characteristics of the PW as PCM with various mass fractions (0.5, 1.0, and 2.0 wt%). They observed that the highest paraffin's thermal conductivity (0.298 W/m K) is achieved at 2.0 wt%. Kalbande et al. [25] carried out the addition of CuO and multi-walled carbon

nanotubes (MWCNT) hybrid nanoparticles into the PW for thermal energy storage applications. They found that the thermal conductivity of nano-enhanced paraffin wax (PCM) was 6.125% higher than that of pure paraffin wax. Harikrishnan et al. [26] investigated the effect of dispersed hybrid nanoparticles CuO-TiO₂ into PW, which includes several mass concentrations of 0.25%, 0.5%, 0.75%, and 1 wt% to improve its thermal performance. They reported that the optimum studied concentration of hybrid nano-phase change material (HnPCM) is 1.0 wt%, and the improvement of thermal conductivity reaches 46.81% compared to pure paraffin. Ibrahim et al. [27] added nano-TiO₂, nano-MgO, and a 50% mixture of the two kinds into PW at different mass fractions of 0.25%, 0.5%, 0.75%, and 1 wt% to find the maximum thermal storage characteristics of PCM. They observed that the highest enhancement is achieved when adding 1% of the nanoparticles, and the thermal conductivity at this fraction is 4.6%, 3.9%, and 4.6% for nano-TiO₂, nano-MgO, and hybrid nanoparticles, respectively.

In this work, the experimental investigations were conducted thoroughly to analyze the variation of thermo-physical properties of paraffin wax based as PCM under the influence of various weight concentrations (1%, 3%, 5%) of the nanoparticles, namely: Cu₂O and Al₂O₃. It is very important to mention here that Cu₂O nanoparticles are used for the first time, as authors know, to improve the thermal properties of paraffin wax. A thorough investigation into the impact of additional hybrid nanoparticles on the thermo-physical properties of paraffin is also rare in the literature. Therefore, the hybrid nanoparticles were also prepared by mixing equal masses of Cu₂O and Al₂O₃ to study their effect on the thermo-physical characteristics of the PCM. It was found that the hybrid nanoparticles at a mass fraction of 5.0 wt% presented significant potential for enhancing the thermal storage properties of the paraffin wax.

2. Experimental work

In this study, the effect of adding Cu₂O, Al₂O₃ nanoparticles, and hybrid Cu₂O-Al₂O₃ nanoparticles into PW under different mass fraction concentrations (1%, 3%, 5%) on its thermal characteristics has been studied. To determine the accurate weights of pure PW, Cu₂O, Al₂O₃, and hybrids of the two nanoparticles, a digital balance with an accuracy of 0.0001 g was employed. Using a water bath, 100 g of pure PW was melted at a melting point of 56 °C in order to prepare a specific PW/nanocomposite to obtain paraffin/nano-Cu₂O (NPCM-1), paraffin/nano-Al₂O₃ (NPCM-2) and paraffin/hybrid nano-Cu₂O-Al₂O₃ (1:1) (NPCM-3) as shown in **Table 1**. After the completely melted PW, nano-Cu₂O, nano-Al₂O₃ and hybrid nanoparticles were added to the PW individually under continuous stirring for around 15 min to reduce the precipitation of the droplet's nano-additives into the PW and make the mixture homogenous. These steps were repeated at each of the nano-additives with various mass concentrations (1%, 3%, 5%). All samples are allowed to cool at room temperature and then shaped into a disc shape in the press designed for this process, where all prepared samples of PW, NPCM-1, NPCM-2, and NPCM-3 were impressed at 15 mm diameter and 3 mm thickness, as shown in **Figure 1**. The thermal properties of PW before and after adding the nano-additive materials were measured using the

Hot Disc Transient (Hot Disc TPS 500 S). Repeating the test twice produces more accurate, very flexible, fast, non-destructive, and reliable thermal properties of PW before and after adding the nano-additive materials, including thermal conductivity, thermal diffusivity, and specific heat. The size of the samples must be determined when a suitable disc radius for a particular material has been chosen and the best test times for the disc and material combination are known. Taking into consideration that the nickel spiral sensor 7577 has a radius of 2.1 mm with Kapton insulation sandwiched between two sample portions to ensure tight contact with the sensor to minimize the amount of air gap. More details about Al_2O_3 nanoparticle preparation and characterization can be found elsewhere [28]. While Cu_2O nanoparticles are purchased from Qualikems Fine Chem Pvt. Ltd., Vadodara, Gujarat, India.

Table 1. Sample labelling and compositions.

S. No.	Sample label	Composition (wt%)
1	Pure paraffin	100 PW
2	1% NPCM-1	99 PW + 1.0 Nano- Cu_2O
3	3% NPCM-1	97 PW + 3.0 Nano- Cu_2O
4	5% NPCM-1	95 PW + 5.0 Nano- Cu_2O
5	1% NPCM-2	99 PW + 1.0 Nano- Al_2O_3
6	3% NPCM-2	97 PW + 3.0 Nano- Al_2O_3
7	5% NPCM-2	95 paraffin+ 5.0 Nano- Al_2O_3
8	1% NPCM-3	99 PW +0.5 Nano- Cu_2O + 5.0 Nano- Al_2O_3
9	3% NPCM-3	97 PW + 1.5 Nano- Cu_2O + 1.5 Nano- Al_2O_3
10	5% NPCM-3	95 PW + 2.5 Nano- Cu_2O + 2.5 Nano- Al_2O_3



Figure 1. Photograph of the prepared paraffin nanocomposites.

3. Results and discussions

In this section, the measured values of different thermal properties of the prepared samples of pure paraffin and nanocomposites are presented, discussed, and evaluated. The compromise between adding individual or hybrid nanoparticles into the PW is also of great interest in this section.

Figure 2 shows the variation of the thermal conductivity of NPCM-1, NPCM-2, and NPCM-3 with the concentrations. For samples NPCM-1 and NPCM-2, it was observed that the thermal conductivity of samples NPCM-1 and NPCM-2 reaches its peak value of 0.2760 W/m K and 0.2708 W/m K at 3.0% mass fraction of nano- Cu_2O and nano- Al_2O_3 , respectively, with an improvement of 10.98% and 9.27% compared to the measured value for pure PW (0.2457 W/mK). But such a tendency is declined

at 5.0 wt% for both samples. The improvement of thermal conductivity is calculated as:

$$\text{percentage of improvement} = \frac{k_{\text{nanocomposit}} - k_{\text{pure paraffin wax}}}{k_{\text{nanocomposit}}} \times 100,$$

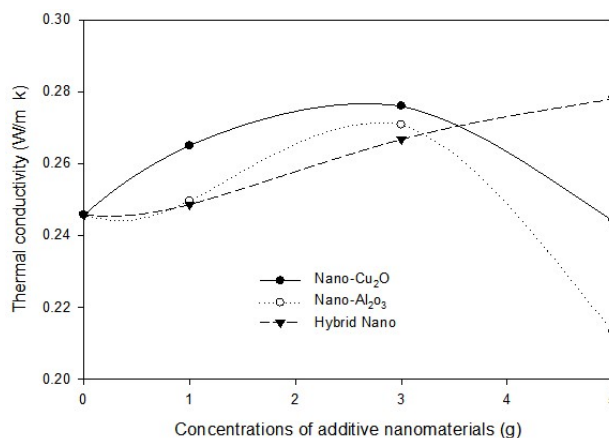


Figure 2. The thermal conductivity of the NEPCMs at different concentrations of 1.0, 3.0 and 5.0 wt%.

The improvement of thermal conductivity of the PW is primarily because these additive nanomaterials have higher thermal conductivity and the combination performance of the nano-additives into the paraffin wax to enable the use of phase-change heat at higher temperatures to enhance the released rate of heat in paraffin. The results of **Figure 2** also show that the thermal conductivity of PW/nano-Cu₂O is higher than that of PW/nano-Al₂O₃ at all studied mass concentrations. While it is higher than those values measured for PW/hybrid nanoparticles except at a mass fraction of 5.0%. This situation of decline happens at higher concentrations (>3%) in NPCM-1 and NPCM-2 samples due to the poor combination between the nano-additives and paraffin, which causes an interfacial thick layer [29], hence augmenting the interface thermal resistance between the paraffin and nano-additives. This layer is unable to contribute to the phase change temperature as phase change does not take place in the interface layer, so it decreases the thermal storage unit volume. Furthermore, the thicker thermal storage layer also diminishes the heat conduction performance of the NEPCMs. The same non-linear trend of thermal conductivity of nano Cu–paraffin composites has been reported by Lin and Al-Kayiem [30]. The results reveal that the increased mass percentage of nanoparticles in the base material may form their repressible agglomeration due to the prevailing cohesive forces, which would account for the diminished slope in the magnitude of thermal conductivity at the upper mass fractions. The phenomenon of an increase and sudden decrease in thermal conductivity of nano-Al₂O₃ was also reported by Arshad et al. [31] due to randomly molecule motion within the disordered microstructure of paraffin in the liquid phase.

The hybrid nano-Cu₂O and nano-Al₂O₃ show different effects as shown in **Figure 2**, where the thermal conductivity increases with increasing the mass fraction (under the studied values) to reach 0.2780 W/m K at a mass concentration of 5.0% compared to 0.2441 W/mK and 0.2133 W/mK for nano-Cu₂O and nano-Al₂O₃, respectively. This improvement achieved by adding hybrid nanomaterials is considered the best among

the studied cases, reaching 11.62% compared to pure paraffin. Keep in mind that this improvement was achieved at a higher concentration (5.0%). The results of **Figure 2** also show that the improvement percentages of the thermal conductivity of paraffin/nano-Cu₂O, paraffin/nano-Al₂O₃ and paraffin/hybrid nanoparticles at 1.0 wt% are 7.28%, 1.56%, and 1.17%, respectively, compared to pure paraffin. While these improvements reached 10.98%, 9.27%, and 7.87%, respectively, at a mass concentration of 3.0% compared to pure paraffin. The results also showed a drop of 0.65% and 13.19% in the thermal conductivity of PW/nano-Cu₂O and PW/nano-Al₂O₃ at 5.0 wt%, respectively. **Figure 2** also shows that the thermal conductivity improvement for PW/nano-Cu₂O is higher by about 5.8% and 1.88% than for PW/nano-Al₂O₃ and PW/hybrid nanoparticles, respectively, at mass fraction 1%, while these percentages increase to 6.19% and 3.37%, respectively, when mass fraction 3.0 wt% is used. On the other hand, the thermal conductivity of PW/hybrid nanoparticles at 5 wt% is higher than the corresponding measured values of PW/nano-Cu₂O and PW/nano-Al₂O₃, which are 12.19% and 23.27%, respectively.

Among the physical properties, thermal diffusivity is considered one of the most important properties because it measures the facility of a material to conduct thermal energy, corresponding to its ability to store thermal energy. Considering the fact that thermal diffusivity has a great significance in thermal management, this property was investigated in the current study, as shown by the results presented in **Figure 3**. This figure shows that the thermal diffusivity of samples NPCM-1 and NPCM-2 reach their maximum values of 0.1595 m²/s and 0.1252 m²/s at 3.0% mass fraction of nano-Cu₂O and nano-Al₂O₃, respectively, compared to 0.1130 m²/s for pure paraffin. So the maximum improvements achieved by adding nano-Cu₂O and nano-Al₂O₃ are 29.15% and 9.74%, respectively, compared to pure paraffin. Accordingly, the thermal conductivity is directly proportional to the thermal diffusivity, so the behavior observed in thermal diffusivity is the same in thermal conductivity. Increasing the mass fraction of nano additives causes an increase in the thermal diffusivity except at concentrations of 5.0 wt% for each of the nano-Cu₂O and nano-Al₂O₃ where the decline occurs, decreasing to 0.1006 and 0.0692 m²/s, respectively, in comparison to pure paraffin.

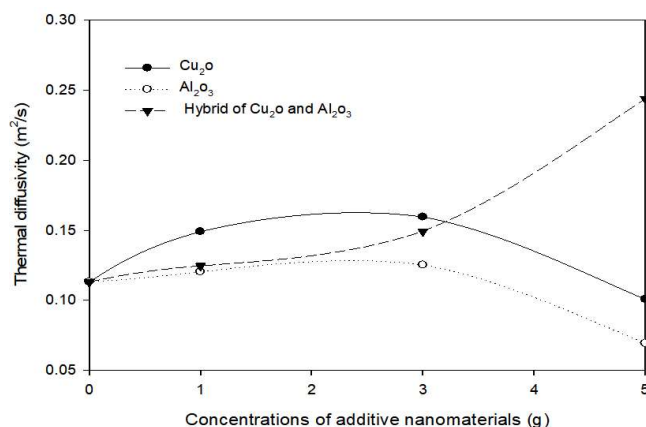


Figure 3. The thermal diffusivity of the NEPCMs at different concentrations of 1.0, 3.0 and 5.0 wt%.

From the results of **Figure 3**, the thermal diffusivity enhanced to 0.1245 m²/s, 0.1493 m²/s and 0.2440 m²/s at 1.0, 3.0, and 5.0 wt%, respectively. In comparison to nano-Al₂O₃ and hybrid nano, the paraffin wax/nano-Cu₂O composite exhibits a percentage improvement of 19.21% and 16.39% at a weight concentration of 1% and 21.50% and 6.39% at a weight concentration of 3%, respectively, as shown in **Figure 3**. However, the hybrid nano has a percentage rise of 58.77% and 71.64% greater than nano-Cu₂O and nano-Al₂O₃ at a weight concentration of 5.0%, respectively. This means that the higher the dispersion of suspended nanoparticles, the higher the thermal diffusivity, which accelerated heat transmission from the top to the bottom of the nanocomposite. The limited dispersion of suspended nanoparticles will affect the value of thermal diffusivity, which will create a reduced heat transfer rate even though the ratio of added nanoparticles is higher. The comparison between the thermophysical properties of all established samples is summarized in **Table 2**.

Table 2. Enhanced thermal properties of the pure paraffin wax.

Samples	Thermal conductivity (W/mk)	Percentage of enhancement (%)	Thermal diffusivity(m ² /s)	Percentage of enhancement (%)
Pure paraffin	0.2457	-	0.1130	-
1% NPCM-1	0.2650	7.28	0.1489	24.11
3% NPCM-1	0.2760	10.98	0.1595	29.15
5% NPCM-1	0.2441	-	0.1006	-
1% NPCM-2	0.2496	1.56	0.1203	6.07
3% NPCM-2	0.2708	9.27	0.1252	9.74
5% NPCM-2	0.2133	-	0.0692	-
1% NPCM-3	0.2486	1.17	0.1245	9.24
3% NPCM-3	0.2667	7.87	0.1493	24.31
5% NPCM-3	0.2780	11.62	0.2440	53.69

The specific heat is the only measured property that decreased with the nano-Cu₂O, nano-Al₂O₃ and hybrid additions into PW as it is inversely proportional to the thermal conductivity and diffusivity as shown in the following equation:

$$\alpha = \frac{k}{\rho c_p} m^2/s.$$

where α and k are thermal diffusivity (m²/s), and thermal conductivity (W/m k), respectively, ρ is the density (Kg/m³) and c_p is specific heat (J/m³k).

The reduction rates as shown in **Figure 4** were 15.52%, 20.88%, 2.31%, and 2.80% for the addition of nano-Cu₂O and nano-Al₂O₃ at concentrations of 1.0 and 3.0 wt%, respectively, in comparison to pure paraffin. According to the decrease in thermal conductivity and also thermal diffusivity for nano-Cu₂O and nano-Al₂O₃ at 5.0 wt%, the specific heat increased to 2.427 J/m³k, 3.081 J/m³k, respectively, which equals 2.1739 J/m³k for pure paraffin. As shown in **Figure 4** the peak reduction percentage is 48.43%, compared to pure paraffin in the case of hybrid nanoparticles at 5.0 wt%. Since the specific heat capacity of nano-Cu₂O is lower than that of nano-Al₂O₃ by about 13.52%, 18.60%, and 21.23% at 1.0, 3.0, and 5.0 wt%, respectively. The same conclusion is revealed by Kok [32]. The author integrated paraffin wax as

PCM with alumina (Al_2O_3) and copper oxide (CuO). His results showed that copper oxide has a lower specific heat capacity than alumina. Also, the influence of the occupied volume variation of nanoparticles immersed into the paraffin was studied by Sushobhan and Kar [33]. Their results agree with the present work since the specific heat of the composites decreased by increasing the volume fraction of nanomaterials through the composite.

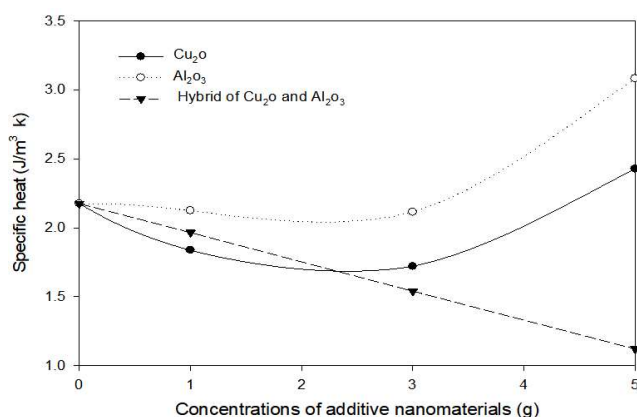


Figure 4. The specific heat of the NEPCMs at different concentrations of 1.0, 3.0 and 5.0 wt%.

From the above results, the hybrid nano- $\text{Cu}_2\text{O}-\text{Al}_2\text{O}_3$ paraffin wax composite at a concentration of 5 wt% is the best among the studied NEPCMs in this work for thermal energy storage systems because it has the highest thermal conductivity and diffusivity. It also has the lowest specific heat, which is considered a good feature in this case as it quickly reaches the melting point.

4. Conclusions

In this study, high-thermal-conductive nano-additives materials were used to prepare NEPCMs by adding different concentrations of Cu_2O , Al_2O_3 , and a mixture of the two oxides in a ratio of 1:1 into the paraffin wax. In general, adding high thermally conductive nano-additives increases the thermal conductivity and thermal diffusivity of the paraffin nano-oxide composites while decreasing the specific heat in comparison to pure paraffin. The peak values of thermal conductivity and diffusivity are achieved at a weight concentration of 3.0% when nano- Cu_2O and nano- Al_2O_3 are added to paraffin wax with significant superiority for nano- Cu_2O . While both of those thermal properties are negatively affected by increasing the concentration beyond this value. The results also showed the excellence of the proposed hybrid nanoparticles compared to nano- Cu_2O and nano- Al_2O_3 , as they achieved the highest values of thermal conductivity and diffusivity at a weight concentration of 5.0 wt%. It also has the lowest specific heat among the studied samples at a weight concentration of 5.0%. Increasing the weight concentration in the case of hybrid nanoparticles may lead to more improvement in the thermal properties. So, it is strongly recommended for future work to study the proposed hybrid nanoparticles of paraffin wax at higher weight concentrations.

Author contributions: Conceptualization, SMS, AAES and MRIR; methodology, SAE; software, ARES; formal analysis, NS; investigation, NS; data curation, NS; writing—original draft preparation, NS; writing—review and editing, SMS; visualization, ARES; supervision, AAES, SAE, MRIR, SMS; project administration, AAES. All authors have read and agreed to the published version of the manuscript.

Acknowledgments: This paper is based upon work supported by Science, Technology and Innovation Funding Authority (STIFA), Capacity building project, Code: 42922.

Conflict of interest: The authors declare no conflict of interest.

References

1. He B, Setterwall F. Technical grade paraffin waxes as phase change materials for cool thermal storage and cool storage systems capital cost estimation. *Energy Conversion and Management*. 2002; 43(13): 1709-1723.
2. Wang J, Xie H, Xin Z, et al. Enhancing thermal conductivity of palmitic acid based phase change materials with carbon nanotubes as fillers. *Solar Energy*. 2010; 84(2): 339-344. doi: 10.1016/j.solener.2009.12.004
3. Shi S, Niu J, Wu Z, et al. Experimental and numerical investigation on heat transfer enhancement of vertical triplex tube heat exchanger with fractal fins for latent thermal energy storage. *International Journal of Heat and Mass Transfer*. 2022; 198: 123386. doi: 10.1016/j.ijheatmasstransfer.2022.123386
4. Fukai J, Hamada Y, Morozumi Y, Miyatake O. Improvement of thermal characteristics of latent heat thermal energy storage units using carbon-fiber brushes: Experiments and modeling. *International Journal of Heat and Mass Transfer*. 2003; 46(23): 4513-4525.
5. Ahmed F, Mahmood M, Waqas A, et al. Thermal analysis of macro-encapsulated phase change material coupled with domestic gas heater for building heating. *Sustainable Energy Technologies and Assessments*. 2021; 47: 101533. doi: 10.1016/j.seta.2021.101533
6. Rehman OA, Palomba V, Verez D, et al. Experimental evaluation of different macro-encapsulation designs for PCM storages for cooling applications. *Journal of Energy Storage*. 2023; 74: 109359. doi: 10.1016/j.est.2023.109359
7. Wang Z, Zhang H, Dou B, et al. Effect of copper metal foam proportion on heat transfer enhancement in the melting process of phase change materials. *Applied Thermal Engineering*. 2022; 201: 117778. doi: 10.1016/j.applthermaleng.2021.117778
8. Leong KY, Hasbi S, Ku Ahmad KZ, et al. Thermal properties evaluation of paraffin wax enhanced with carbon nanotubes as latent heat thermal energy storage. *Journal of Energy Storage*. 2022; 52: 105027. doi: 10.1016/j.est.2022.105027
9. Summers EK, Lienhard JH. Experimental study of thermal performance in air gap membrane distillation systems, including the direct solar heating of membranes. *Desalination*. 2013; 330: 100-111. doi: 10.1016/j.desal.2013.09.023
10. Yang Y, Luo J, Song G, et al. The experimental exploration of nano-Si₃N₄/paraffin on thermal behavior of phase change materials. *Thermochimica Acta*. 2014; 597: 101-106. doi: 10.1016/j.tca.2014.10.014
11. Wang J, Li Y, Wang Y, et al. Experimental investigation of heat transfer performance of a heat pipe combined with thermal energy storage materials of CuO-paraffin nanocomposites. *Solar Energy*. 2020; 211: 928-937. doi: 10.1016/j.solener.2020.10.033
12. Pise AT, Waghmare AV, Talandage VG. Heat Transfer Enhancement by Using Nanomaterial in Phase Change Material for Latent Heat Thermal Energy Storage System. *Asian Journal of Engineering and Applied Technology*. 2013; 2(2): 52-57. doi: 10.51983/ajeat-2013.2.2.667
13. Ho CJ, Gao JY. Preparation and thermophysical properties of nanoparticle-in-paraffin emulsion as phase change material. *International Communications in Heat and Mass Transfer*. 2009; 36(5): 467-470. doi: 10.1016/j.icheatmasstransfer.2009.01.015
14. Zhao Y, Jin L, Zou B, et al. Expanded graphite – Paraffin composite phase change materials: Effect of particle size on the composite structure and properties. *Applied Thermal Engineering*. 2020; 171: 115015. doi: 10.1016/j.applthermaleng.2020.115015
15. Sari A, Karaipekli A. Thermal conductivity and latent heat thermal energy storage characteristics of paraffin/expanded graphite composite as phase change material. *Applied Thermal Engineering*. 2007; 27(8-9): 1271-1277. doi: 10.1016/j.applthermaleng.2006.11.004

16. Huang YR, Chuang PH, Chen CL. Molecular-dynamics calculation of the thermal conduction in phase change materials of graphene paraffin nanocomposites. *International Journal of Heat and Mass Transfer*. 2015; 91: 45-51. doi: 10.1016/j.ijheatmasstransfer.2015.07.110
17. Maher H, Rocky KA, Bassiouny R, et al. Synthesis and thermal characterization of paraffin-based nanocomposites for thermal energy storage applications. *Thermal Science and Engineering Progress*. 2021; 22: 100797. doi: 10.1016/j.tsep.2020.100797
18. Jawad QA, Mahdy AMJ, Khuder AH, et al. Improve the performance of a solar air heater by adding aluminum chip, paraffin wax, and nano-SiC. *Case Studies in Thermal Engineering*. 2020; 19: 100622. doi: 10.1016/j.csite.2020.100622
19. Pradeep N, Paramasivam K, Rajesh T, et al. Silver nanoparticles for enhanced thermal energy storage of phase change materials. *Materials Today: Proceedings*. 2021; 45: 607-611. doi: 10.1016/j.matpr.2020.02.671
20. Şahan N, Fois M, Paksoy H. Improving thermal conductivity phase change materials—A study of paraffin nanomagnetite composites. *Solar Energy Materials and Solar Cells*. 2015; 137: 61-67. doi: 10.1016/j.solmat.2015.01.027
21. Mhedheb T, Hassen W, Mhimid A, et al. Parametric analysis of a solar parabolic trough collector integrated with hybrid-nano PCM storage tank. *Case Studies in Thermal Engineering*. 2023; 51: 103652. doi: 10.1016/j.csite.2023.103652
22. Hayat MA, Yang Y, Li L, et al. Preparation and thermophysical characterisation analysis of potential nano-phase transition materials for thermal energy storage applications. *Journal of Molecular Liquids*. 2023; 376: 121464. doi: 10.1016/j.molliq.2023.121464
23. Manoj Kumar P, Mylsamy K, Alagar K, et al. Investigations on an evacuated tube solar water heater using hybrid-nano based organic phase change material. *International Journal of Green Energy*. 2020; 17(13): 872-883. doi: 10.1080/15435075.2020.1809426
24. Pasupathi MK, Alagar K, P MJS, et al. Characterization of Hybrid-nano/Paraffin Organic Phase Change Material for Thermal Energy Storage Applications in Solar Thermal Systems. *Energies*. 2020; 13(19): 5079. doi: 10.3390/en13195079
25. Kalbande VP, Fating G, Mohan M, et al. Experimental and theoretical study for suitability of hybrid nano enhanced phase change material for thermal energy storage applications. *Journal of Energy Storage*. 2022; 51: 104431. doi: 10.1016/j.est.2022.104431
26. Harikrishnan S, Deepak K, Kalaiselvam S. Thermal energy storage behavior of composite using hybrid nanomaterials as PCM for solar heating systems. *Journal of Thermal Analysis and Calorimetry*. 2013; 115(2): 1563-1571. doi: 10.1007/s10973-013-3472-x
27. Ibrahim SI, Ali AH, Hafidh SA, et al. Stability and thermal conductivity of different nano-composite material prepared for thermal energy storage applications. *South African Journal of Chemical Engineering*. 2022; 39: 72-89. doi: 10.1016/j.sajce.2021.11.010
28. Abosheisha HF, Mansour DEA, Darwish MA, et al. Synthesis and investigation of structural, thermal, magnetic, and dielectric properties of multifunctional epoxy/Li_{0.5}Al_{0.35}Fe_{2.15}O₄/Al₂O₃ nanocomposites. *Journal of Materials Research and Technology*. 2022; 16: 1526-1546. doi: 10.1016/j.jmrt.2021.11.149
29. Mahian O, Kolsi L, Amani M, et al. Recent advances in modeling and simulation of nanofluid flows-Part I: Fundamentals and theory. *Physics Reports*. 2019; 790: 1-48. doi: 10.1016/j.physrep.2018.11.004
30. Lin SC, Al-Kayiem HH. Evaluation of copper nanoparticles – Paraffin wax compositions for solar thermal energy storage. *Solar Energy*. 2016; 132: 267-278. doi: 10.1016/j.solener.2016.03.004
31. Arshad A, Jabbal M, Yan Y. Thermophysical characteristics and application of metallic-oxide based mono and hybrid nanocomposite phase change materials for thermal management systems. *Applied Thermal Engineering*. 2020; 181: 115999. doi: 10.1016/j.applthermaleng.2020.115999
32. Kok B. Examining effects of special heat transfer fins designed for the melting process of PCM and Nano-PCM. *Applied Thermal Engineering*. 2020; 170: 114989. doi: 10.1016/j.applthermaleng.2020.114989
33. Sushobhan BR, Kar SP. Thermal Modeling of Melting of Nano based Phase Change Material for Improvement of Thermal Energy Storage. *Energy Procedia*. 2017; 109: 385-392. doi: 10.1016/j.egypro.2017.03.035