

ORIGINAL RESEARCH ARTICLE

Genesis of Langrial Iron Ore of Hazara area, Khyber Pakhtunkhwa, Pakistan

Naghmah Haider^{1*}, Sajjad Khan¹, Rehanul Haq Siddiqui², Shahid Iqbal³, Nazar-Ul-Haq¹

¹Geoscience Advance Research Laboratories, Geological Survey of Pakistan, P.O Box No. 1461, Shahzad Town, Islamabad 45600, Pakistan. E-mail: naghma.haider@gmail.com

²Balochistan University of Information Technology, Engineering and Management Sciences, Quetta 87300, Pakistan.

³Department of Earth Sciences, Quaid e Azam University, Islamabad 45600, Pakistan.

ABSTRACT

In this paper, a detailed mineralogical and genesis investigation have been carried out in the seven locations of the Iron Ore in Hazara area. Thick bedded iron ore have been observed between Kawagarh Formation and Hangu Formation i.e, Cretaceous-Paleocene boundary. At the base of Hangu Formation, variable thickness of these lateritic beds spread throughout the Hazara and Kohat-Potwar plateau. This hematite ore exists in the form of unconformity. X-ray diffraction technique (XRD), X-ray fluorescence spectrometry (XRF), detailed petrographic study and scanning electron microscope (SEM) techniques indicated that those iron bears minerals including hematite, chamosite and quartz, albite, clinocllore, illite-montmorillonite, kaolinite, calcite, dolomite, whereas ankerite are the impurities present in these beds. The X-ray fluorescence (XRF) results show that the total Fe₂O₃ ranges from 39 to 56%, with high silica and alumina ratio of less than one. Beneficiation requires for significant increase in ore grade. The petrographic study revealed the presence of ooids fragments as nuclei of other ooids with limited clastic supply, which indicate high energy shallow marine depositional setting under warm and humid climate. The overall results show that Langrial Iron Ore is a low-grade iron ore which can be upgraded up to 62% by applying modern mining techniques so as to fulfill steel requirements of the country.

Keywords: Langrial Iron Ore; Cretaceous-Paleocene Boundary; Geochemistry; Hazara Area; Hangu Formation

ARTICLE INFO

Article history:

Received 15 July 2021

Received in revised form 25 August 2021

Accepted 30 August 2021

Available online 6 September 2021

COPYRIGHT

Copyright © 2021 Naghmah Haider *et al.*

doi:10.24294/jgc.v4i2.740

EnPress Publisher LLC. This work is licensed under the Creative Commons Attribution-NonCommercial 4.0 International License (CC BY-NC 4.0).

<https://creativecommons.org/licenses/by-nc/4.0/>

1. Introduction

Iron ore plays a significant role in the development of modern society, which can be used to extract iron, steel and manufacture other alloys. Iron usually occurs in a number of geological environments from deep seated basic igneous intrusion to late stage hydrothermal igneous and metamorphic and sedimentary environment^[1]. Iron occurs in banded sedimentary rocks of Precambrian age as residual or replacement deposits. Iron also occurs as oolitic ironstone in Paleozoic to Cretaceous sedimentary successions of the world. The reported massive iron ores in Precambrian igneous rocks of Kirana Hills are magnetite and hematite^[2]. Pyrometamorphic deposits formed due to replacement of limestone or volcanic rocks by magnetite.

Occurrences of iron ores are widespread in Pakistan. Mainly these are along unconformities, volcanogenic ores or contact metasomatic deposits. Iron ores have been reported from Indus platform zone, Foreland sedimentary belt, Himalayan crystalline belt, Ophiolitic thrust belt and Chagai magmatic arc^[1]. Massive iron ore of Precambrian

age from Kirana Hills near Sargodha consist of magnetite and hematite^[2,3].

In Himalayas Foreland Fold and Thrust Belt (HFFTB) of Pakistan, ironstones of oolitic textures are mainly reported in Mesozoic to early Tertiary formations^[2,4-6].

The main objective of the study is to explain the texture, mineralogy and depositional environment of the Langrial iron ore in Hazara-Abbottabad area.

2. Geological and tectonic framework

The Hazara area forms the western limb of the Hazara Kashmir Syntax (HKS) and appears as a crescent shape in the northwestern margin of the Indo-Pakistani subcontinent with a North-East to South-East trending. The crescent shaped Hazara area is bounded by Panjal Thrust and the Main

Boundary Thrust (MBT) and number of local thrust faults that lie in a similar NE-SW trend (**Figure 1**).

The oldest rock unit of the area is Precambrian Hazara Formation represented by Hazara Group Slates and sedimentary rocks^[7]. Hazara Formation is unconformably overlain by Abbottabad Formation of Cambrian age composed of quartzose sandstone, shale, siltstone, limestone and dolomite^[8]. Overlain Mesozoic sedimentary rocks are represented by Samana Suk Formation of Jurassic age and Cretaceous Lumshiwal and Kawagarh Formation^[8,9].

The Paleocene Lockhart Formation is lying above the ironstone beds and Cretaceous Kawagarh Formation (**Table 1**) is lying below the Ironstone beds^[8,10,11]. The Hangu Formation is overlain by the Lockhart Limestone^[8,10,11]. Iron beds also exist at places in the cores of both limbs of anticlines of Paleocene Lockhart Limestone.

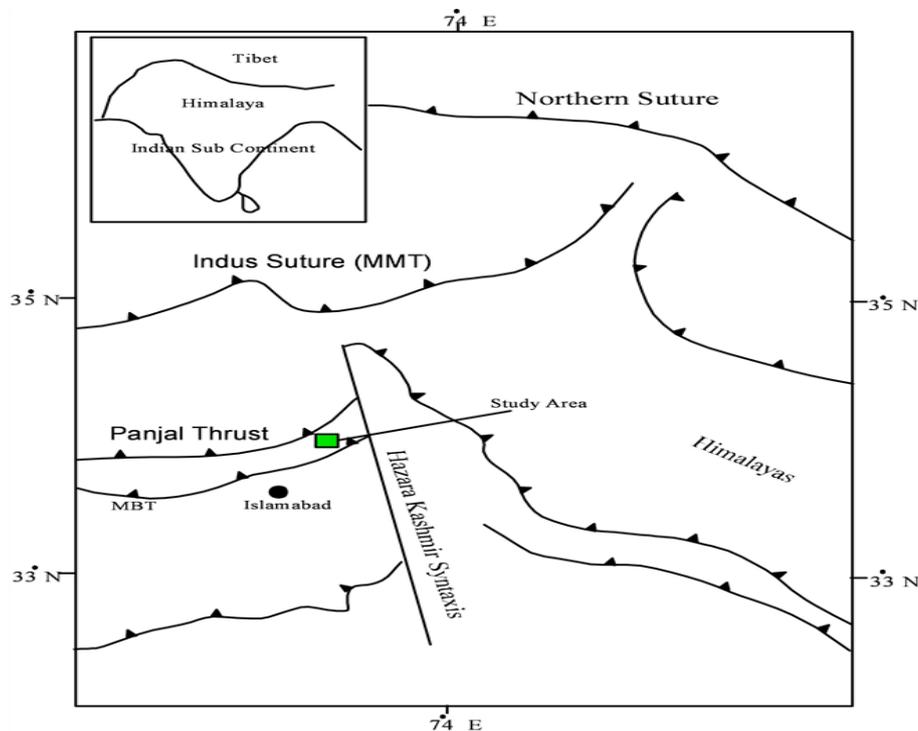


Figure 1. Tectonic sketch map of northern Pakistan^[12].

Table 1. Lithostratigraphic unit of the Hazara-Abbottabad area^[8]

Age	Formation	Description
Paleocene	Lockhart Limestone	Limestone dark grey to black in colour and contains intercalations of marl and shale.
Paleocene to Cretaceous	Oolitic Iron beds	Oolitic hematite mixed with chamosite, limonite.
Upper Cretaceous	Kawagarh Formation	Grey, olive grey, light grey sub-lithographic limestone with subordinate with marl and calcareous shale.
Upper Cretaceous	Lumshiwal Formation	Thick bedded to massive, light grey current bedded sandstone with silty, sandy, glauconitic shale towards the base.
Pre-Cambrian	Hazara Formation	Slate, phyllite and shale with minute occurrences of limestone and graphite layers.

3. Materials and methods

During reconnaissance survey, seven stratigraphic sections, namely, Bagnotar, Bagan, Durban and Langrial, Danna Noral, Tati Maira, Najaf Pur and Jabri were selected for a detailed study. The study area spreads for about 32 kilometers to the

south of Abbotabad. Sedimentary features and orientation and thickness of iron ore beds were examined and 65 samples were collected marked by Global Positioning System (GPS) for subsequent laboratory analysis (**Figure 2**). Bagnotar (Siri) area is located between $34^{\circ}56'10''$ N and $73^{\circ}20'$ E.

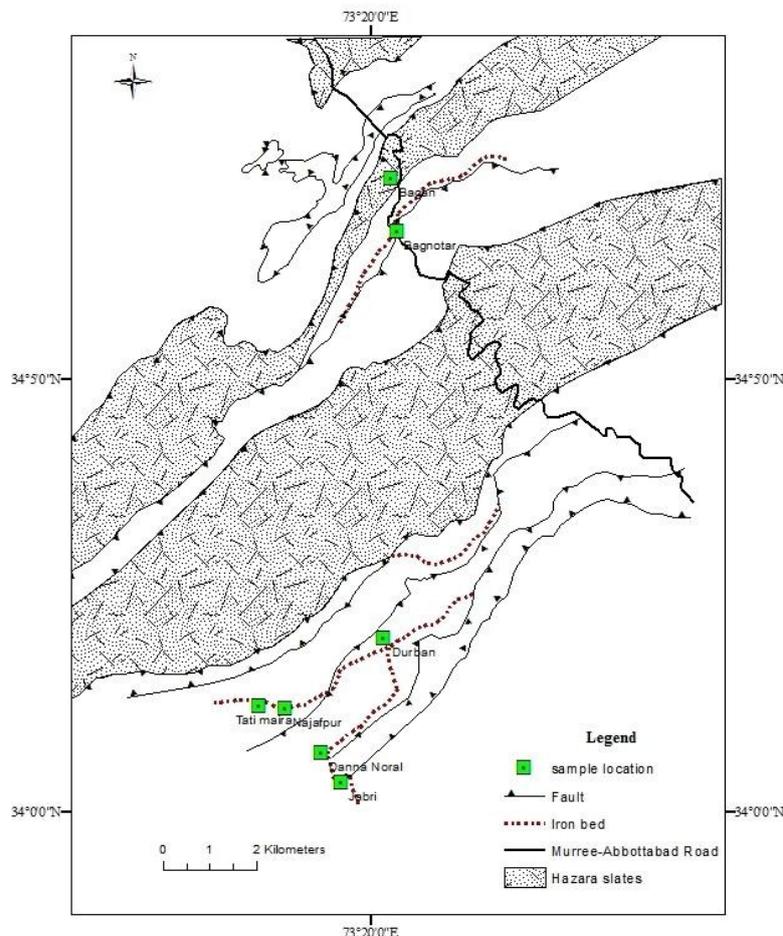


Figure 2. Location map showing geology of the study area.

The strike of the bed is $N10^{\circ}$ E with a dip varying from 32° SW to 35° SE. Iron bed of 1.5m to 2m have been reported. Iron beds exhibit oolitic to pisolitic hematitic to goethitic appearances, overlain and underlain by Lockhart Limestone due to tectonic disturbance in the area.

Bagan lies between $34^{\circ}58'$ N and $73^{\circ}20'01''$ E. The strike of the bed is $N60^{\circ}$ W with a dip of 20° to 45° NE. The thrust contact between the iron ore and Lockhart formation is observed.

At Durban and Langrial area, the samples have been collected at $34^{\circ}15'$ N and $72^{\circ}17'01''$ E. The strike of the bed is $N35^{\circ}$ E and dip is 40° SE. Highly fractured thin to medium bedded iron ore of 2 meter thickness are noted.

Jabri area lies between $34^{\circ}03'01''$ N and $73^{\circ}17'$

$01''$ E. The strike of the bed is $N60^{\circ}$ E and dip is 30° SE. Thin to medium bedded laterite have been reported in this area.

Danna Noral is located between $34^{\circ}08'$ N and $72^{\circ}21'$ E. The strike and dip of the bed are $N60^{\circ}$ E, 25° SE respectively. Upper part of iron ore is Kawagarh formation with strike $N45^{\circ}$ E and 10° SW dip. The thickness of unconformity (i.e., conglomeratic beds) varies from 0.15m to 0.6m at different localities. Upper contact of iron beds is unconformable with Kawagarh formation marked by ferruginous conglomerates whereas the lower contact is sharp with greenish grey to brown flaky shale, the deposit form a synclinal structure.

Tati Maira is located between $34^{\circ}06'$ N and $73^{\circ}19'01''$ E with a $N30^{\circ}$ E strike and a 25° NW dip

where presents lateritic beds. Najaf Pur area lies between 34°11'04" N and longitude 72°15'01" E with N60° W beds strike and dip 55° SW. The Upper part of the Iron Ore consists of nodular limestone of Lockhart Formation. At Sardhana village near Najafpur, the iron beds show anticline and syncline structure.

3.1 Petrographic techniques

Thin sections and polished slabs of selected samples are prepared at sample preparation section of the Geoscience Advance Research Laboratory, Geological Survey of Pakistan, Islamabad for the Petrographic study under camera fitted Nikon made reflected light polarizing microscope at different magnifications.

3.2 X-ray diffraction analysis

The selected samples were crushed at the crushing and powdering section of Geoscience Advance Research Laboratory of the Geological Survey of Pakistan, Islamabad. The analysis was carried out by Panalytical X'PertPRO Diffractometer (XRD) at 45 Kv and 40 mA with CuK α radiations scanning speed at 0.05°/Sec scanned by X'Pert data collector software and identified with the help of its matching peaks with the existing data base (**Figure 3**).

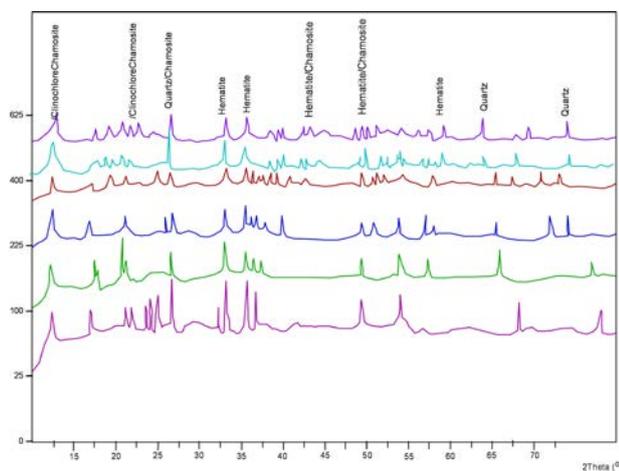


Figure 3. XRD pattern of selected powder samples, where dominant peaks are labeled.

3.3 Scanning electron microscope analysis

Thin section of selected samples was analyzed using scanning electron microscope (Model JEOL JSM 6610LV) to study microscopic structures (**Figure 4**). Compositional analyses were carried out

using EDS (OXFORD X-MAX 20mm²). Carbon coating is well applied to the thin section to avoid charging of the particles during observation.

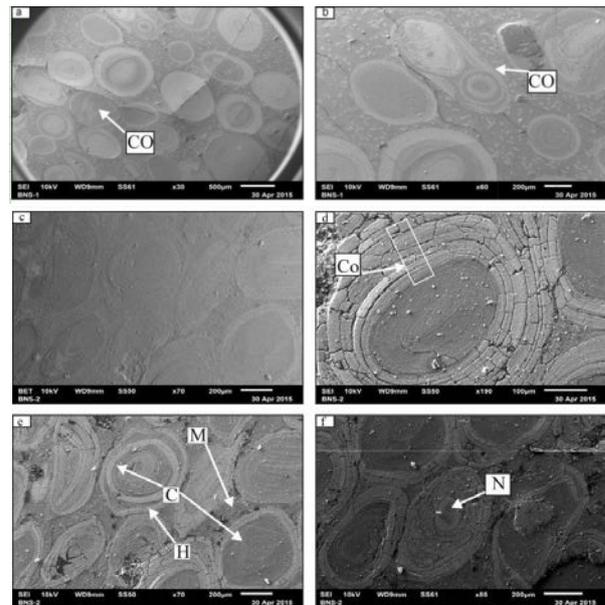


Figure 4. Scanning electron microscopic (SEM) images of the iron ore thin section. **a, c, e)** concentric and elliptical ooids; **b)** composite ooid; **d, f)** concentric lamination in cortex of the ooids. (**Note:** CO is composite ooids; Co is cortex; C is Chamosite; H is hematite; M is matrix and N is nucleus.)

3.4 X-ray fluorescence spectrometry

The chemistry of selected samples were analyzed by using Panalytical Axios WD-XRF for all major element using fundamental parameter method with the help of glass bead by taking 1:10 ratio of volatile free sample and lithium tetra borate.

4. Results and discussion

Petrographic and Mineralogical study by XRD indicates the most prominent iron minerals are hematite and chamosite (**Figure 5**). After interpretation of mineral on XRD with the help of its crystal system and d-spacing values, other minerals are quartz, albite, chamosite, clinocllore, illite-montmorillonite, kaolinite, calcite, dolomite and ankerite (**Figure 3**).

XRD study has direct influence on the commercial value of the ore and processing of the ore regarding carbon footprint and coal consumption. The study of the gangue minerals is necessary for taking steps for beneficiation of ores. According to results of X-ray diffraction analysis, it can be safely suggested that all ore samples from studied area were observed to be mainly of a hematitic nature.

Certain localities like Danna Noral and Najafpur shows hematite ores with iron content (40-50% Fe), such hematite deposits require little beneficiation.

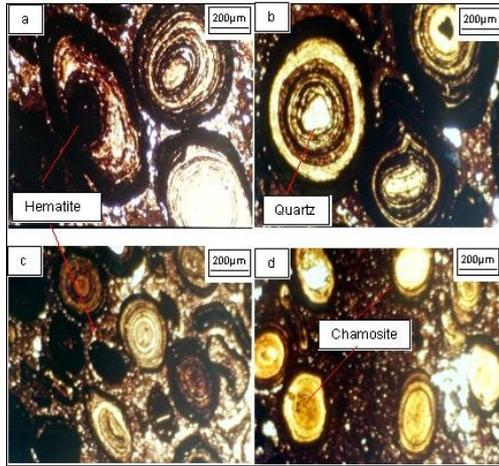


Figure 5. Photomicrographs of selected samples collected from the study area showing **a)** concentric ooids with hematite and chamosite rich concentric lamination. **a & d)** Elongated ooids due to early compaction. **b)** Nucleus of oolites consists of quartz, feldspars, hematite and rock fragments. **c & d)** ooids consist of pure hematite whereas others are comprised of entirely chamosite.

The geochemical analysis shows high silica content in the iron ore from Bagnotar area as compared to Danna Noral and Najafpur (**Tables 2 and 3; Figure 6**). SiO₂ ranges between 9-35% here, it is necessary to mention that three samples BNS-4, 9 and 10 belongs to Lockhart Limestone having low SiO₂ and Al₂O₃ varies between 10-18%. Beneficiation requires for reducing high alumina content. Crushing, scrubbing and washing of iron ores techniques are being adopted to reduce alumina in some extent^[13].

The total Fe₂O₃ ranges from 37.2 to 72.74%. Average iron (Fe) concentration in samples from Bagnotar area is 37.89%. The trace constituents are calcium, magnesium, sodium, potassium, manganese, and phosphorus oxides. These are low-grade iron ore which can be upgraded up to 62% by applying modern mining techniques^[14].

Table 2. Chemical composition of samples collected from Bagnotar area

	BNS-1	BNS-2	BNS-3	BNS-5	BNS-6	BNS-7	BNS-4	BNS-9	BNS-10
SiO ₂	20.24	17.32	18.52	28.04	27.46	23.3	14.53	6.20	0.00
TiO ₂	0.7	0.45	0.42	0.63	0.79	0.58	0.14	0.348	0.065
Al ₂ O ₃	12.44	10.53	10.46	10.98	17.63	11.88	0.56	2.04	1.18
Fe ₂ O ₃	48.25	54.21	56.31	45.06	39.45	45.24	2.81	4.40	3.68
MnO	0.04	0.1	0.08	0.13	0.03	0.03	0.26	0.04	0.189
MgO	2.58	2.31	2.28	2.27	2.0	2.01	7.42	7.77	0.62
CaO	4.12	3.06	2.62	3.07	2.98	2.96	37.3	42.13	52.5
Na ₂ O	0.23	0.77	0.39	0.31	0.13	0.41	0.25	0.00	0.08
K ₂ O	0.09	0.1	0.14	0.17	0.21	0.07	0.18	0.86	0.26
P ₂ O ₅	1.34	1.41	1.41	1.17	0.7	1.10	0.03	0.009	0.124
SO ₃	-	-	-	-	0.08	-	-	0.90	0.025
LOI	9.88	9.27	7.36	8.17	9.28	12.43	36.53	35.00	41.30
Fe	33.73	37.89	39.36	31.50	27.58	31.62	1.96	3.08	2.57
Al/Si	0.61	0.60	0.56	0.39	0.64	0.51	-	-	-

Table 3. Chemical composition of samples collected from Danna Noral, Najafpur Jabri and Tatimaira areas

	DN-29	DN-30	DN-31	NF-62	NF-63	NF-64	JB-26	JB-27	TM-33	TM-34
SiO ₂	12.51	12.61	9.75	21.04	11.37	13.54	18.72	19.49	35.38	30.76
TiO ₂	0.84	0.68	0.27	0.84	0.52	0.55	0.60	0.57	0.54	0.51
Al ₂ O ₃	9.70	10.30	7.62	18.84	8.47	10.79	7.31	12.71	10.02	10.53
Fe ₂ O ₃	63.93	59.13	72.74	37.20	69.73	57.75	52.94	50.58	38.82	46.59
MnO	0.02	0.02	0.01	0.04	0.53	0.05	0.01	0.30	0.16	0.09
MgO	1.55	1.50	1.19	4.79	2.65	3.20	1.78	3.47	1.31	1.29
CaO	2.29	5.80	1.32	1.26	3.34	3.54	1.05	1.09	1.79	2.20
Na ₂ O	0.48	0.25	0.38	2.11	0.00	0.18	1.94	0.0	2.12	0.0
K ₂ O	0.02	0.02	0.03	-	0.01	-	0.04	-	0.02	0.02
P ₂ O ₅	1.53	1.37	0.78	0.24	0.55	2.41	0.15	0.30	1.08	1.38
LOI	7.15	8.32	5.91	13.65	8.64	7.99	15.96	13.22	8.78	9.33
Fe	44.69	41.33	50.85	26.00	48.74	40.37	37.01	35.36	27.14	32.57
Al/Si	0.77	0.82	0.78	0.89	0.74	0.79	0.39	0.65	0.28	0.34

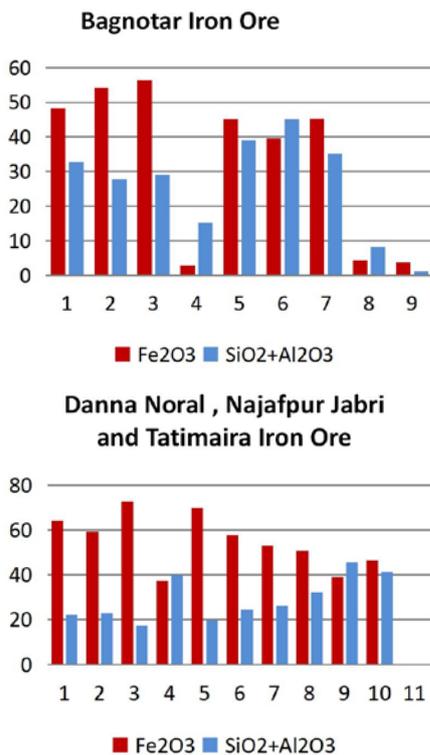


Figure 6. Iron, aluminum and silica ratios of selected samples collected from northern part, Bagnotar area and southern part including Danna Noral, Najafpur Jabri and Tati Maira areas.

Samples from Danna Noral (41-50% Fe) contain high iron content as compare to the Najafpur (26-48% Fe), Jabri (35-37% Fe) and Tati Maira (27-32% Fe). Concentration of SiO₂ and Al₂O₃ are also low as compared to Bagnotar area. The beneficiation should require gravity separation as well as magnetic separation in Langrial Iron ore deposits.

The adverse effects of high alumina to silica ratio (ideally it should be < 1) is harmful to blast furnace as well as sinter plant^[13]. Aluminum silica ratio in our samples is less than 1, which is good for beneficiation (Table 2 and 3), while alumina raises the melting point of slag and increases fuel consumption in the furnace.

Microscopic mineralogical studies indicated that hematite is the major iron oxide mineral with quartz and chamosite. XRD studies revealed hematite as the major minerals with subordinate amounts of quartz, albite, chamosite, clinocllore, illite-montmorillonite, kaolinite, calcite, dolomite and Ankerite confirming the microscopic findings.

These oolites consist of concentric layers of the iron and iron rich clays chamosite, so these deposits contain an iron oxide hematite with iron clay (chamosite). The photo micrographs show that the

ratio between hematite and chamosite varies. Thus, some ooids consist of almost pure hematite (Figure 5c) whereas others are comprised of almost entirely chamosite (Figure 5d). The nucleus of the ooids are variable and consist of quartz, as well as feldspars, iron oxides, broken pieces of older ooids and other rock fragments (Figure 5b). These compositional variation are also noted through back scattered image of scanning electron microscope (Figure 4).

The presence of ooids fragments as nuclei of other ooids indicates that the formations of ooids are the product of a high energy shallow marine environment with limited clastic sediment supply.

5. Depositional settings

The hematite-chamositic composition of the deposits indicates intense chemical weathering under humid continental conditions^[15]. Such conditions are usually common in humid equatorial settings^[16]. Paleo-geographic reconstruction studies indicate that the area occupied an equatorial position during the deposition of the Langrial iron ore^[10]. Ooids are generally considered to be the product of high energy shallow water and agitated environment. Such oolitic texture is the characteristic of the Phanerozoic iron deposits^[17]. These ooids consist of concentric rings of iron bearing minerals and are formed by chemical process in sedimentary rocks^[18]. The presence of oolitic ironstones usually shows high relative sealevel, warm and humid climate as well as favored chemical weathering^[10,19,20]. In the study area, the iron ores occur in the lower part of the Palaeocene Hangu Formation. In the Salt and Surghar ranges, this lower part of the Hangu Formation is interpreted to have been deposited in terrestrial conditions, while the upper part of the formation indicates transitional settings with the overlying marine Lockhart Limestone^[21]. On the contrary, recent studies have interpreted shallow marine and deltaic environment of deposition for the lower part of the Hangu Formation^[16]. The present study reports abundance bioturbation and biogenic activity. Further, abundance of burrowing in the sandstone of the Hangu Formation, to go with the presence of marine fossils in the formation indicates marine deposition^[22,23]. However, brackish water pollens of the palm genus *Spinizonocolpites*

are reported from the lower part in these areas^[16]. Strong influence of subaerial exposure and lateritic palaeosol development is indicated for the Langrial iron ore^[16]. A rise in relative groundwater base level may have triggered swampy/boggy land formation to spread over lateritic paleosol deposits that formed on weathered paleo-surfaces of the Cretaceous/older strata^[16]. In addition, tectonic controls probably combined with eustatic and climatic controls, influenced the development of the laterites in the area^[24].

The tropical, humid climatic conditions coupled with intense chemical weathering produced the initial Fe-rich material, probably as amorphous hydroxides or goethite during the lateritization processes. Marine transgression along the continental margin favored the preservation of these sediments^[10]. The high PCO₂, probably associated with the Deccan Trap basalts^[25] may have created a stratified ocean with reducing conditions and negative Eh. Such conditions favor Siderite (FeCO₃) precipitation, a phenomena also identified in modern oolitic ironstone samples, precipitating at negative Eh, (under reducing conditions) and low sulfide activity (PS₂-) in sediment pore-waters^[18,26,27]. However, since there are abundant dissolved sulfates dissolved in marine water, thus low sulfide activity is rarely attained in marine sediments. Further, the Deccan trap activity may also have contributed to additional amount of sulfur in the atmosphere. Hence the initial form of the iron oolite sediment appeared to have been accumulated under non-marine or brackish conditions^[10].

Further, the bacterial decomposition of the organic matter, following the Cretaceous/Palaeogene mass extinction event may have created/added to the anoxic conditions that accommodate siderite precipitation^[28]. The diagenetic processes, following the formation and consolidation of the initial ooids, may have then converted these into hematite-chamosite ooids^[29]. The episodic basaltic volcanic activity of the Deccan Trap may have created a fluctuating oxic to anoxic conditions^[28] that were favorable for the formation of chamosite ((Mg,Fe)₃Fe₃(Si₃Al)O₁₀(OH)₈), without sulfide activity as the sulfur rich aerosols settle quickly from the atmosphere^[18,30]. These conditions also provided the op-

portunity for the hematite precipitation as the latter is stable under moderate to strong oxidizing conditions^[18,26]. These fluctuating environmental conditions must have had a strong control on the depositional and early diagenetic history of the Langrial Iron Ore.

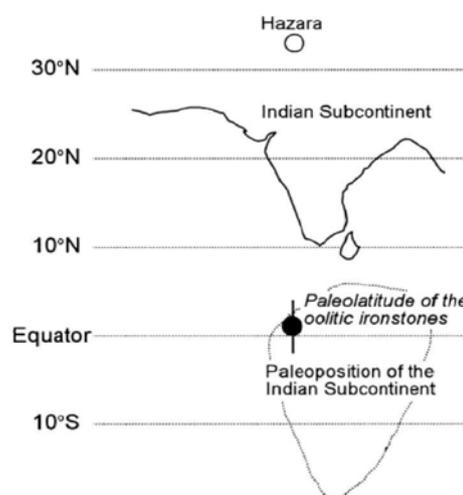


Figure 7. Fluctuating environmental conditions of Hazara area.

6. Conclusion

Langrial Iron Ore occurs in the basal part of Hangu Formation of Paleocene age mainly of hematitic nature with gangue minerals. The deposits are low grade Iron ore mostly consisting of hematite and chamosite in nature with an average Fe₂O₃ content of 52.37%. The mineralogical and petrological interpretation indicated that the deposit was formed under warm humid climate. This low grade iron ore has silica aluminum ratio of less than 1, which is good for beneficiation. Langrial Iron Ore has economic significance proved by combined petrographical, geochemical and mineralogical data and the value can be further increased by the application of modern metallurgical processing technologies. The oolitic layers vary in numbers and will lead to a high difficulty to separate iron from gangue minerals in the oolitic structure. It is necessary to carry out a very fine grinding to achieve the mineral separation. These deposits show potential to be economically viable in the present market.

Conflict of interest

The authors declare that they have no conflict of interest.

Acknowledgments

The author thanks to Dr. Imran Khan, Director of the General Geological Survey of Pakistan for providing field and laboratory facilities. Sincere gratitude would also be extended to Mr. Syed Ishtiaq Khan and Mrs. Nousheen Firdos in the Geological Survey of Pakistan for their helping in Laboratory work.

References

1. Kazmi AH, Abbas SG. Metallogeny and mineral deposits of Pakistan. Islamabad: Orient Petroleum Inc.; 2001. p. 88–150.
2. Maynard JB. Geochemistry of sedimentary ore deposits. New York: Springer-Verlag; 1983. p. 305.
3. Maynard JB. Geochemistry of sedimentary ore deposits. Springer Science & Business Media; 2012.
4. Ahmad Z. Directory of mineral deposits of Pakistan. Geological Survey of Pakistan (Karachi) 1969; 15: 1–220.
5. Hallam A, Maynard JB. The iron ores and associated sediments of the Chichali Formation (Oxfordian to Valanginian) of the Trans-Indus Salt Range, Pakistan. *Journal of the Geological Society* 1987; 144(1): 107–114.
6. Garzanti E. Himalayan ironstones, “superplumes”, and the breakup of Gondwana. *Geology* 1993; 21(2): 105–108.
7. Middlemiss CS. The geology of Hazara and the Black mountain. Geological Survey of India, *Memoirs* 1896; 26: 302.
8. Shah SMI. Stratigraphy of Pakistan. *Memoir of the Geological Survey of Pakistan* 2009; 22: 121–132.
9. Kazmi AH, Abbasi IA. Stratigraphy & historical geology of Pakistan. Peshawar: Peshawar Publication; 2008. p. 245–263.
10. Yoshida M, Khan IH, Ahmad MN. Remanent magnetization of oolitic ironstone beds, Hazara area, Lesser Himalayan thrust zone, Northern Pakistan: Its acquisition, timing, and paleoenvironmental implications. *Earth Planets Space* 1998; 50: 733–744.
11. Fatmi AN. Lithostratigraphic units of the Kohat-Potwar Province, Indus Basin, Pakistan. *Memoirs of the Geological Survey of Pakistan* 1974; 10: 1–80.
12. Kazmi AH, Jan MQ. Geology and tectonics of Pakistan. Nazimabad: Graphic publishers; 1997. p. 77–121.
13. Rao DS, Kumar VTV, Rao SS, *et al.* Mineralogy and geochemistry of a low grade iron ore sample from Bellary-Hospet Sector, India and their implications on beneficiation deposits. *Journal of Minerals and Materials Characterization and Engineering* 2009; 8(2): 115–132.
14. Muwanguzi AJB, Karasev AV, Byaruhanga JK, *et al.* Characterization of chemical composition and microstructure of natural iron ore from Muko deposits. *ISRN Materials Science* 2012; 2012: 1–9.
15. Boggs S Jr. Petrology of sedimentary rocks. 2nd ed. Cambridge, England, Hardback: Cambridge University Press; 2009. p. 600.
16. Warwick PD, Javed S, Mashhadi STA, *et al.* Lithofacies and palynostratigraphy of some Cretaceous and Paleocene rocks, Surghar and Salt Range coal fields, northern Pakistan. Washington, DC: U.S. Government Publishing Office; 1995. p. 1–35.
17. Young TP. Phanerozoic ironstones: An introduction and review. Geological Society, London, Special Publications 1989; 46(1): ix–xxv.
18. Tucker ME. Sedimentary Petrology. 2nd ed. Oxford: Blackwell Science; 1991. p. 260.
19. Gilbert JM, Park CF Jr. The geology of ore deposits. New York: Waveland Press; 1986. p. 985.
20. Blatt H, Middleton G, Murray R. Origin of sedimentary rocks. 2nd ed. Englewood Cliffs: Prentice-Hall Inc.; 1980. p. 782.
21. Danilchik W, Shah SMI. Stratigraphy and coal resources of the Makarwal area, Trans-Indus Mountains, Mianwali District, Pakistan. United States Geological Survey, Professional Paper; (USA) 1987; 75 (1341): 38.
22. Davies LM, Pinfold ES. Eocene beds of the Punjab Salt Range. *Memoirs of the Geological Survey of India* 1935; 24(1): 79.
23. Haque AFMM. The foraminifera of the Ranikot and Laki of Nammal Gorge, Salt Range. *Memoirs of the Geological Survey of Pakistan, Paleontologia Pakistanica* 1956; 1: 1–300.
24. Shah SHA. Stratigraphic observations of laterites in Pakistan and oscillation and movement of the Eurasian and Indian blocks. *Geological Bulletin of the University of Peshawar* 1984; 17: 101–108.
25. Schoene B, Samperton KM, Eddy MP, *et al.* U-Pb geochronology of the Deccan Traps and relation to the end-Cretaceous mass extinction. *Science* 2015; 347(6218): 182–184.
26. Krauskopf KB, Bird DK. Introduction to geochemistry. New York: McGraw-Hill; 1967. p. 721.
27. Harder H. Mineral genesis in ironstones: A model based upon laboratory experiments and petrographic observation. Geological Society, London, Special Publications 1989; 46: 9–18.
28. Schulte P, Alegret L, Arenillas I, *et al.* The Chicxulub asteroid impact and mass extinction at the Cretaceous-Paleogene boundary. *Science* 2010; 327(5970): 1214–1218.
29. Crowe SA, Roberts JA, Weisener CG, *et al.* Alteration of iron-rich lacustrine sediments by dissimilatory iron-reducing bacteria. *Geobiology* 2007; 5(1): 63–73.
30. Kimberley MM. Origin of oolitic iron formations. *Journal of Sedimentary Research* 1979; 49(1): 111–131.